


## DIN EN 1401 – 1 / Plastics Piping Systems for non-Pressure Underground Drainage and Sewerage –Unplasticized Poly(vinyl chloride) (PVC-U) –Part 1: Specifications for Pipes, Fittings and the System / Testing Equipment

### Description

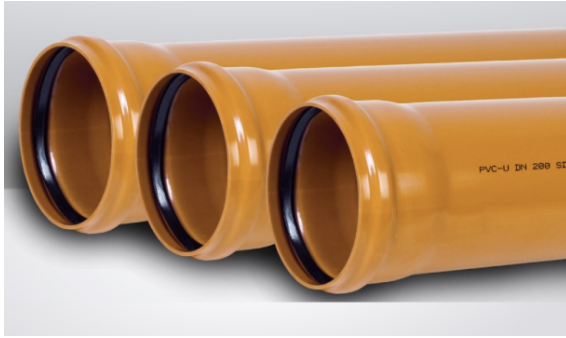

#### 4.2 Pipe material

When tested in accordance with the test method as specified in Table 1, using the indicated parameters, the pipe material shall have characteristics conforming to the requirements given in Table 1.

The pipe material shall be tested in the form of a pipe.

Table 1 — Material characteristics of pipes

Characteristic	Requirements	Test parameters		Test method
Resistance to internal pressure	No failure during the test period	End caps	Type A or B conforming to EN ISO 1167-1:2006	EN ISO 1167-1:2006
		Test temperature	60 °C	
		Orientation	Free	
		Number of test pieces	3	
		Circumferential (hoop) stress	10 MPa	
		Conditioning period	1 h	
		Type of test	Water-in-water	
		Test period	1 000 h	

#### 4.3 Fitting material

When tested in accordance with the test method as specified in Table 2, using the indicated parameters, the fitting material shall have characteristics conforming to the requirements given in Table 2.

The fitting material shall be tested, in the actual formulation, in the form of an extruded or injection-moulded pipe. Fabricated fittings or parts of fabricated fittings shall be made from pipes conforming to this European Standard, except for the requirements for the wall thickness, and/or mouldings from

PVC-U which conform to material, mechanical and physical characteristics as required in this European Standard.

**Table 2 — Material characteristics of fittings**

Characteristic	Requirements	Test parameters		Test method
Resistance to internal pressure	No failure during the test period	End caps Dimensions Free length for injection-moulded pipe Test temperature Orientation Number of test pieces Circumferential (hoop) stress Conditioning period Type of test Test period	Type A or B conforming to EN ISO 1167-1:2006 $50 \text{ mm} \leq d_n \leq 110 \text{ mm}$ $3 \text{ mm} \leq e \leq 5 \text{ mm}$ $\geq 140 \text{ mm}$ 60 °C Free 3 6,3 MPa 1 h Water-in-water 1 000 h	EN ISO 1167-1:2006

## 7 Mechanical characteristics

### 7.1 Mechanical characteristics of pipes

#### 7.1.1 General requirements

When tested in accordance with the test method as specified in Table 9 using the indicated parameters, the pipe shall have general mechanical characteristics conforming to the requirements given in Table 9.

**Table 9 — General mechanical characteristics of pipes**

Characteristic	Requirements	Test parameters		Test method
Impact resistance <sup>a</sup> (round-the-clock method)	TIR ≤ 10 %	Test/conditioning temperature Conditioning medium Type of striker  Mass of striker for: $d_n = 110 \text{ mm}$ $d_n = 125 \text{ mm}$ $d_n = 160 \text{ mm}$ $d_n = 200 \text{ mm}$ $d_n = 250 \text{ mm}$ $d_n \geq 315 \text{ mm}$  Fall height of striker for: $d_n = 110 \text{ mm}$ $d_n \geq 125 \text{ mm}$	0 °C Water or air $d/90$ conforming to EN 744:1995  1,0 kg 1,25 kg 1,6 kg 2,0 kg 2,5 kg 3,2 kg  1 600 mm 2 000 mm	EN 744:1995
<sup>a</sup> If the manufacturer chooses to use indirect testing (see prCEN/TS 1401-2:2007 [1]), the preferred temperature is (23 ± 2) °C.				

### 7.2 Mechanical characteristics of fittings

When tested in accordance with the test methods as specified in Table 11 using the indicated parameters, the fitting shall have mechanical characteristics conforming to the requirements given in Table 11.

Table 11 — Mechanical characteristics of fittings

Characteristic	Requirements	Test parameters		Test method
Mechanical strength or flexibility <sup>a</sup>	No sign of splitting, cracking, separation, and/or leakage	Test period Minimum moment for [DN] ≤ 250 [DN] > 250 or Minimum displacement	15 min $0,15[DN]^3 \times 10^{-6}$ kNm 0,01[DN] kNm 170 mm	EN 12256
Impact strength (drop test)	No damage	Test/conditioning temperature Fall height for $d_n = 110$ mm $d_n = 125$ mm $d_n = 160$ mm $d_n = 200$ mm Point of impact	0 °C 1 000 mm 1 000 mm 500 mm 500 mm Mouth of the socket	EN 12061
<sup>a</sup> Only for fabricated fittings made from more than one piece. A sealing ring retaining means is not considered as a piece.				

## 8 Physical characteristics

### 8.1 Physical characteristics of pipes

When tested in accordance with the test methods as specified in Table 12 using the indicated parameters, the pipe shall have physical characteristics conforming to the requirements given in Table 12.

Table 12 — Physical characteristics of pipes

Characteristic	Requirements	Test parameters		Test method
Vicat softening temperature (VST)	≥ 79 °C	Shall conform to EN 727		EN 727
Longitudinal reversion	≤ 5 % The pipe shall exhibit no bubbles or cracks	Test temperature Immersion time for: $e \leq 8$ mm $e > 8$ mm	150 °C 15 min 30 min	EN ISO 2505: Liquid bath
		or Test temperature Immersion time for: $e \leq 4$ mm $4 \text{ mm} < e \leq 16$ mm $e > 16$ mm	150 °C 30 min 60 min 120 min	EN ISO 2505: Air oven
Resistance to dichloromethane at a specified temperature	No attack <sup>a</sup>	Test temperature Immersion time	15 °C 30 min	EN 580
<sup>a</sup> Isolated spots less than 2 mm shall not be considered an attack.				
NOTE if a more detailed investigation on the gelation level is wanted, ISO 18373-1 and ISO 18373-2 [4] can be used.				

### 8.2 Physical characteristics of fittings

When tested in accordance with the test methods as specified in Table 13 and Table 14 if applicable

using the indicated parameters, the fitting shall have physical characteristics conforming to the requirements given in Table 13 and/or Table 14, as applicable.

**Table 13 — Physical characteristics of fittings**

Characteristic	Requirements	Test parameters		Test method
Vicat softening temperature (VST)	$\geq 77\text{ }^{\circ}\text{C}$ <sup>a</sup>	Shall conform to EN 727		EN 727
Effects of heating	<sup>b</sup> and <sup>c</sup>	Test temperature Heating time for: $e \leq 10\text{ mm}$ $e > 10\text{ mm}$	150 $^{\circ}\text{C}$  30 min 60 min	EN ISO 580: Air oven
<sup>a</sup> VST $\geq 79\text{ }^{\circ}\text{C}$ for application area code "D" and for $d_n$ less than or equal to 200 mm. <sup>b</sup> 1) within a radius of 15 times the wall thickness around the injection point(s), the depth of cracks, delamination or blisters shall not exceed 50 % of the wall thickness at that point; 2) within a distance of 10 times the wall thickness from the diaphragm zone, the depth of cracks, delamination or blisters shall not exceed 50 % of the wall thickness at that point; 3) within a distance of 10 times the wall thickness from the ring gate, the length of cracks shall not exceed 50 % of the wall thickness at that point; 4) the weld line shall not have opened more than 50 % of the wall thickness at the line; 5) in all other parts of the surface the depth of cracks and delaminations shall not exceed 30 % of the wall thickness at that point. Blisters shall not exceed a length 10 times the wall thickness. <sup>c</sup> After cutting through the fitting, the cut surfaces shall show no foreign particles, when viewed without magnification.				

**Table 14 — Physical characteristics of fabricated fittings**

Characteristic	Requirements	Test parameters		Test method
Watertightness <sup>a</sup>	No leakage	Water pressure Duration	0,5 bar 1 min	EN 1053
<sup>a</sup> Only for fabricated fittings made from more than one piece. A sealing ring retaining means is not considered as a piece.				

## 9 Performance requirements

When tested in accordance with the test methods as specified in Table 15 using the indicated parameters, the joints and the system shall have fitness for purpose characteristics conforming to the requirements given in Table 15.

**Table 15 — Performance requirements**

Characteristic	Requirements	Test parameters		Test method
Tightness of elastomeric sealing ring joints		Test temperature	(23 ± 5) °C	EN 1277, Condition B
		Spigot deflection	10 %	
		Socket deflection	5 %	
	No leakage	Water pressure	0,05 bar	
	No leakage	Water pressure	0,5 bar	EN 1277, Condition C
	≤ -0,27 bar	Air pressure	-0,3 bar	
		Test temperature	(23 ± 5) °C	
		Angular deflection for: $d_n \leq 315$ mm $315 \text{ mm} < d_n \leq 630$ mm $d_n > 630$ mm	2° 1,5° 1°	
	No leakage	Water pressure	0,05 bar	
	No leakage	Water pressure	0,5 bar	
	≤ -0,27 bar	Air pressure	-0,3 bar	
Elevated temperature cycling <sup>a</sup>	No leakage	Shall conform to EN 1055		EN 1055 using test assembly b) (Figure 2)

<sup>a</sup> Test required only for components intended to be used for application area code "D" and for  $d_n$  less than or equal to 200 mm.

### Summary of Testing Equipment

- Dimensional measurement equipment for pipes and fittings
- Mechanical Flexibility EN 12256
- Vicat Softening Point EN 727
- Resistance to Dichloromethane EN 580
- Falling Weight Impact Tester EN 744 / EN 12061
- Longitudinal Reversion (Hot Air Oven) EN ISO 2505
- Water Tightness Tester EN 1053
- Thermal Cycling tester EN 1055
- Hydrostatic Pressure Tester EN ISO 1167-1
- Hot Water Bath for Hydrostatic Pressure Tester EN 921
- SS304 End Caps
- Combinational Test for Seals EN 1277

















### Category

1. Equipment for Standards
2. Standards